

Cds Quantum Dots Composite Sol-gel Rod for Optical Applications

M. Naziruddin KHAN*, Abdullah ALMOHAMMEDI

Department of Physics, Faculty of Science, Islamic University of Madinah-42351, Saudi Arabia

<http://dx.doi.org/10.5755/j02.ms.34175>

Received 22 May 2023; accepted 19 August 2024

Colloidal quantum dots (QDs) based on CdS were directly incorporated into a sol to fabricate solid rods. Various characterization techniques were employed to study the properties of the composite rod. A comparison between the absorption, emission, and excitation spectra of the QDs in the solid rod and in solution revealed their significant and stable nature in the solid state. SEM image shows that QD particles are well interacted with the sol gel environment. The observed particle size of QDs was heteronomous approximately from 5 to 10 nm. The XRD pattern of QDs illustrates their crystalline nature. The significant spontaneous emission (SE) signal was enhanced from QDs composite rod under the excitation of a 355 nm Pico second laser source. These findings suggest that further improvements in the integration of QDs into sol gel rods could be achieved by employing a higher density of QDs in the solid rod. The fabrication of QDs composite rods with a high concentration holds the potential for testing stimulated or amplified spontaneous emission in future studies.

Keywords: CdS QDs composite sol gel, absorption, PL, TEM, spontaneous emission.

1. INTRODUCTION

In recent years, there has been a growing interest in semiconductor nanocrystals known as quantum dots. These quantum dots have unique properties that make them highly attractive, including their ability to absorb light across a wide range of wavelengths [1], their high quantum yield [2] and the size-dependent wavelength of photoluminescence (PL) due to quantum confinement [3–6] due to quantum confinement. Among the different quantum dots, CdS quantum dots (QDs) is one of the important II-VI group of semiconductor compounds which possess size dependent PL and is tunable in the visible range [7]. Therefore, QDs have been interested for many optoelectronic applications, such as light emitting diodes [8, 9], lasers [10], telecommunications [11], and solar energy [12]. Enormous studies on different properties of QDs especially in thin films prepared by various techniques [13–16] were done for many applications. From the optical application point of view, the most interesting property is the PL stability of QDs in an environment. Currently, sol-gel technology has emerged as a promising matrix for embedding semiconductor nanoparticles [17]. This method allows for low-temperature preparation and enables the use of composite materials for diverse applications. A quantum size effect from the CdS sol-gel composite has been observed [18]. Influence of the Cd/S molar ratio on the properties of nanocrystalline CdS doped sol gel thin films has been reported [19]. QDs embedded in a PMMA composite film demonstrated stable emission bands regardless of variations in excitation energy [20].

CdS QDs doped sol gel matrix resulted in the strong luminescence without any casing [21]. QDs embedded silicate glass as an inorganic color converter was observed

with significant stability [22]. Though the significant works of CdS in sol gel matrix have been reported in the literature, most studies of the QDs were either in solutions or composite thin films. In view of the previous studies, the exploration of optical gain from composite QDs is still limited. A research group has successfully fabricated and studied the silicon nanoparticles doped sol-gel rod, ormosil rod [23, 24] and polymer rod [25]. Significant optical stability of the nanoparticles in such matrix rods was observed. Recently, perovskite quantum dots were employed in polymer rods which enhanced the amplified spontaneous emission (ASE) like behavior [26]. In this study, a new approach was adopted in which CdS quantum dots were incorporated into a sol-gel matrix and transformed into solid composite rods. The QDs composite rods were subjected to various optical characterization techniques, and their stimulated emission was tested to evaluate the optical response under a tunable laser system.

2. EXPERIMENTAL DETAILS

A solution of CdS quantum dots (QDs) dispersed in methanol at a concentration of 10 mg/L was obtained from MK Impex Corp., Canada. The QDs were 98 % pure and had a size range of 5–10 nm (APS). The QDs solution was doped in sol gel matrix. In the procedure of sol-gel preparation, the inorganic precursor tetraethylorthosilane (TEOS; Aldrich, 98%) and methanol (Riedel-deHaen) was reacted to form silica sol. Formamide and nitric acid was involved as drying control chemical additive (DCCA) and catalyst respectively. The molar ratio of the sol composition was [1:1.5:0.5:1:0.01], TEOS: methanol: formamide: water: HNO₃ acid respectively. The final sol was further stirred during which the QDs solution was directly encapsulated dropwise. Then the QDs composite sol was poured into some polystyrene test tubes and quartz cuvettes and placed in an oven at 50 °C. The samples slowly became a gel and formed crack free solid in a few

* Corresponding author. Tel.: +966920022042 ext: 6667
E-mail address: mnkhan@iu.edu.sa (M.N. Khan)

weeks. The final product of QDs composite rods was studied using different characterization techniques.

Absorption and emission spectra of the QDs were recorded using a UV-Visible-NIR spectrophotometer (Jasco V-670) and fluorescence spectrometer (Lumina, Thermo) respectively. The crystal structure of the QDs was inspected using XRD equipment PANanalytical X'Pert with Cu-K α radiation ($\lambda = 0.154$ nm). The size and morphological structure of the QDs was examined by HRTEM (JEOL, Model-JEM2100F) and FESEM (JEOL, Model-JSM-6380LA) respectively. The spontaneous emission spectra of the QDs in solution and composites rod were tested by 355 nm laser pulse at the repetition rate of 15 Hz from Q-switched Nd:YAG picosecond tunable laser system (LS-2151, Lotti III) through an optical fiber attached with a spectrograph (QE65 Pro, Ocean Optics). A UV lamp (model XX15NF, Spectroline-USA) was used in this case to obtain images of samples with luminescent emission of QDs.

3. RESULTS AND DISCUSSION

The digital image of the light emitting QDs solution, undoped and doped sol-gel rods under the exposure of UV lamp is displayed in (Fig. 1 a and b).

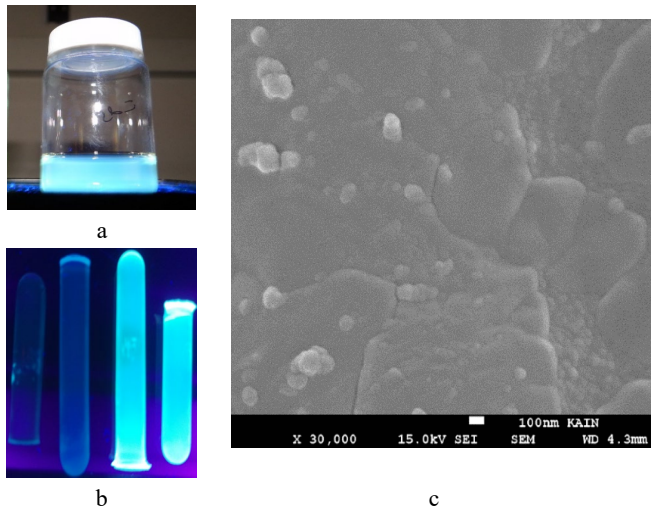


Fig. 1. CdS QDs: a – solution; b – undoped and doped sol gel rods under UV exposure; c – SEM image

The emission of light from the QDs composite rods indicates a well-distributed dispersion of QD particles within the matrix, demonstrating their stability during the sol gel process. The noticeable inhabitant of QD particles

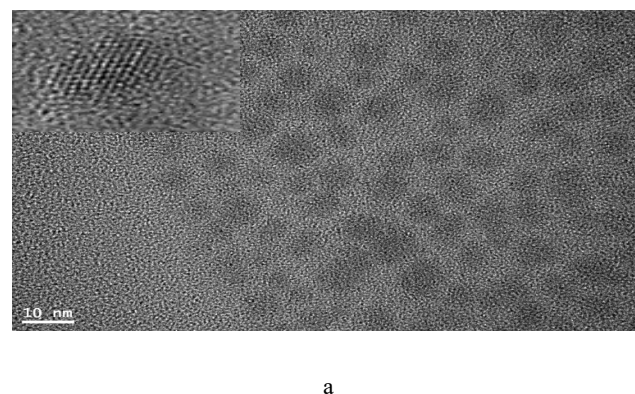


Fig. 2. TEM image of QDs: a – composite sol-gel; b – EDX spectrum

inside the rod environment was confirmed by the image of Scanning Electron Microscopy (SEM) as shown in (Fig. 1 c). Many QD particles are scattered inside the surface layer of sol-gel matrix. The composite surface shows that QD particles are well intermingled with the sol-gel environment. The good interaction of the QDs with the matrix environment could yield a good stable composite material. The size of QD particles was inspected by TEM. Fig. 2 a shows the image of QDs distribution of different size in sol gel environment. The majority of QD particles are well spreading and heteronomous sizes of approximately from 5 to 10 nm. The crystalline nature of the QD particle is seen in (Fig. 2 a-inset). It indicates that there is no agglomeration of particles within the solid environment. In addition, the presence of QD particles in the sol gel is confirmed by EDX spectrum. Cadmium rich with sulfide is seen in the EDX spectrum as displayed in (Fig. 2 b). The typical crystalline nature of QDs in the TEM image is supported by the XRD pattern as shown in (Fig. 3).

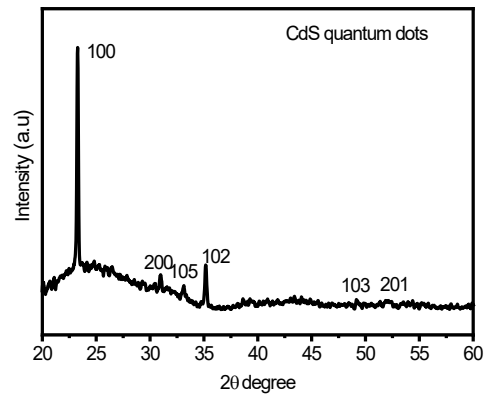
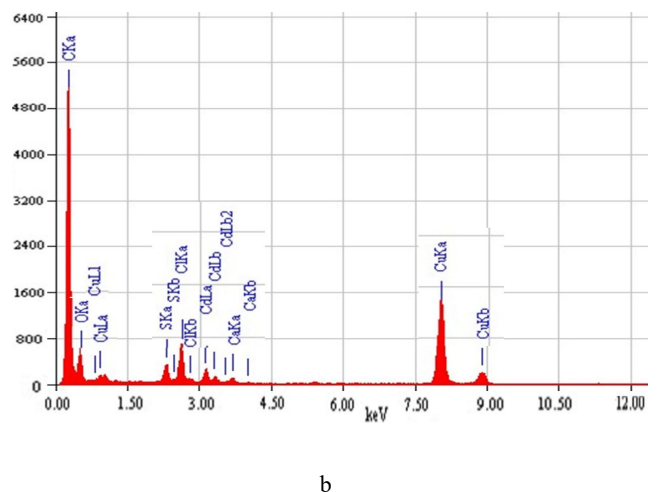


Fig. 3. XRD spectrum of CdS quantum dots

The XRD peaks of QDs indicate crystalline nature. Prominent peaks and few cubic phase of QDs structure are observed at 23.30, 35.12, 49.9, 52.2 deg. corresponding to lattice planes (100), (102), (103) and (201) which correspond to the data from JCPDS file no. 42-1411. The XRD peak at around 31 deg. of CdS QDs shows the presence of cubic phase and corresponds to plane (200) according to the result work [27]. The peak at around 33 deg. may correspond to diffraction plane 105 of the hexagonal phase [28].



To observe the higher absorbance of quantum dots (QDs) in both solution and sol-gel solid rod, the absorption spectra were measured using high (10 mg/L) and low (5 mg/L) concentrations. The results are depicted in (Fig. 4). The enhancement of absorbance with a concentration of QDs is observed in solution and sol-gel rod. The differences in absorbance of QDs between the solvent and sol-gel rod are shown in (Fig. 4). The absorption peak of QDs solution is observed with a shoulder peak at around 315 nm which is supported by the observed absorption peak value at 320 nm of 2.5 nm size [29].

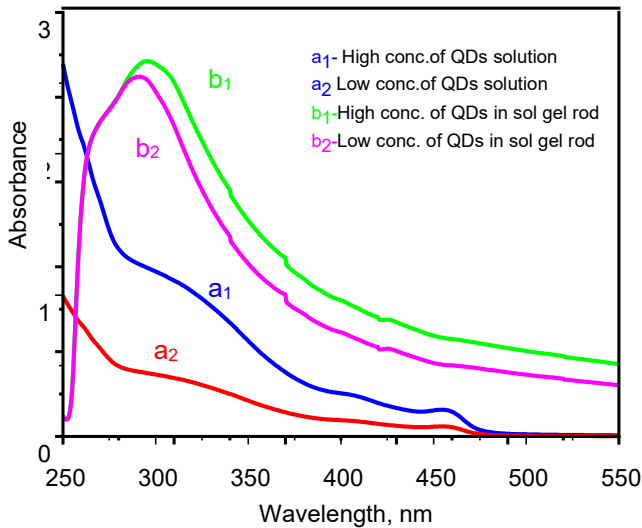


Fig. 4. Absorption spectra of QDs: a₁, a₂–solution; b₁, b₂–sol-gel rod

The two weak absorption peaks of QDs in solution at around 412 nm and 460 nm appeared. The absorbance of the QDs composite sol-gel rod is higher than the solution. But the absorption peak becomes broad with a slightly blue-shift when QDs doped in sol-gel rod as shown in (Fig. 4). There are two absorption peaks observed at around 370 and 420 nm in the sol gel matrix which is

fundamentally weak. The effect of absorption spectra is due to the solid environment of the matrix. In addition, the nature of the distribution of QD particles in sol-gel may affect the absorption property. It is also possible to cause the absorption property of QDs during the transition of phase from sol to solid [25]. Present absorption spectra of QD in sol-gel rod are comparable to the observed feature of CdS particles in xerogel state [30] and hybrid sol gel matrix [21]. The broad particle size distribution within the matrix [30] likely contributes to the effect of QDs in the matrix. In the present study, the sample with high concentration was only employed. The main motive of this work is to understand the PL and SE property of QDs in sol gel rod that could be employed in testing the optical gain. The excitation wavelengths for emission and excitation spectra of QDs were evaluated from 450–650 nm and 300–500 nm respectively. The excitation peaks of the QDs in solution were observed at 395 nm, 418 nm and 465 nm as seen in C₁ and C₂ spectra of (Fig. 5 a).

The excitation wavelengths of the QDs for a solution and sol-gel rod were selected as 355 nm, 395 nm, 418 nm, 465 nm and 355 nm, 378 nm, 418 nm, 460 nm respectively as listed in Table 1. Fig. 5 a, the peaks a₁, a₂, a₃ and a₄, (Fig. 5 b), peaks b₁, b₂, b₃ and b₄ indicate that the emission peak and relative intensity of QDs solution and sol-gel rod are influenced by the excitation wavelengths respectively. This suggests that varying the excitation energy has an impact on the relative intensity of the QDs in both samples. But the change in emission peak of the QDs solution and sol-gel rod by different excitation is not clear but it may be possible to the presence of a large number of heterogeneous QDs size. Moreover, the emission peaks and relative intensity of QDs sol gel rod is considerably changed from the peaks of QDs solution. For instance, the peak observed at 485 nm of QDs solution was excited by the 355 nm wavelength observed at 470 nm in sol-gel rod.

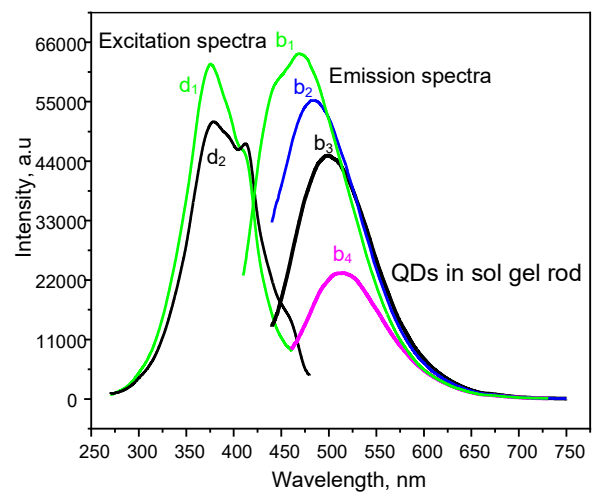
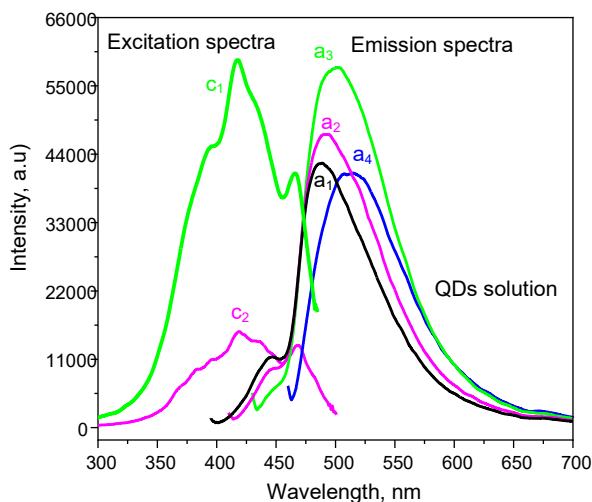


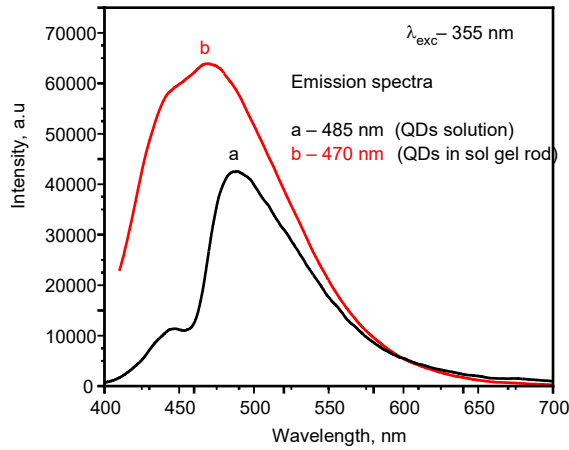
Fig. 5. The emission and excitation spectra of QDs: a–solution; b–sol-gel solid

Table 1. Comparison of peaks between the QDs in solution and sol-gel rod

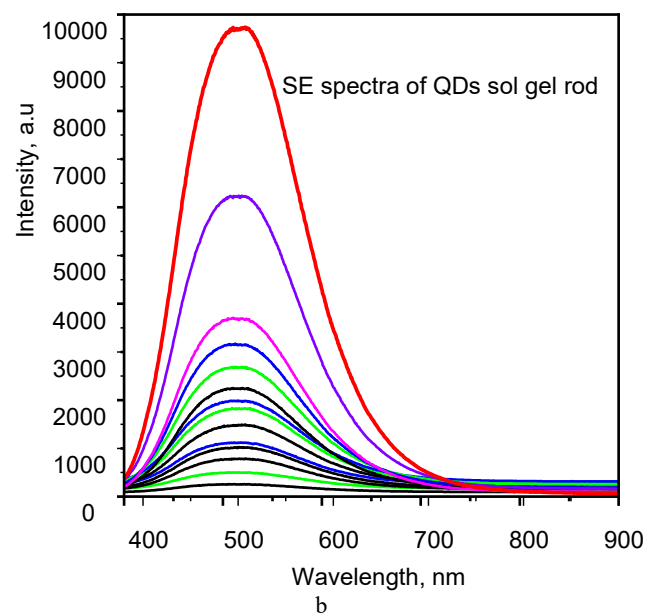
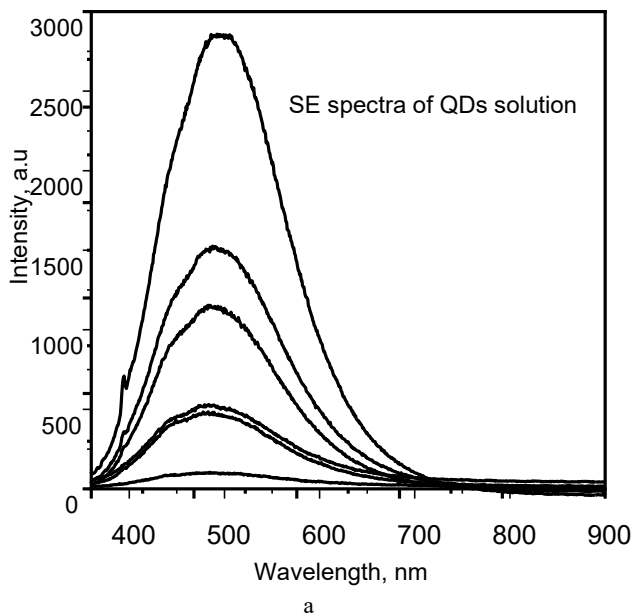
Samples	Absorption peak, nm	Excitation peaks, nm	Emission peaks, nm	Spontaneous emission peaks, nm
QDs Solution	315	395	a ₁ – 485 at λ_{exc} 355	506
	412	418	a ₂ – 492 at λ_{exc} 395	
	460	465	a ₃ – 501 at λ_{exc} 418	
			a ₄ – 510 at λ_{exc} 465	
QDs sol-gel rod	298	378	a ₁ – 470 at λ_{exc} 355	500
	370	412	a ₂ – 483 at λ_{exc} 378	
	420	460	a ₃ – 498 at λ_{exc} 418	
			a ₄ – 512 at λ_{exc} 460	

It means that emission peaks and intensity of QDs are quite caused and enhanced by sol gel solid medium. Similarly, the excitation spectra of the QDs in solution are affected when they are embedded in the sol gel rod. The influences on the emission peaks and band shape of the QDs in the sol gel may be attributed to the solid environment, suggesting that the presence of the sol-gel matrix alters the optical properties of the QDs.

The absorbance and emission intensity of quantum dots (QDs) solution exhibit remarkable stability in comparison to the absorption and emission of QDs in solid rod, as demonstrated in (Fig. 4 and Fig. 6).

**Fig. 6.** The comparison between the emission spectra of QDs solution and sol-gel solid at 355 nm excitation wavelength

When the QDs solution is directly incorporated into a sol and converted into a solid rod, the optical properties of the QDs in the solid rod remain largely unaffected. The comparison of emission spectra between QDs solution and sol-gel rod is displayed in (Fig. 6). No degradation on the emission intensity of QDs in sol-gel rod is observed since the scattering and reflection of light are highly possible within the solid environment. The emission and excitation peak positions of QDs in solution and solid sol-gel are listed in Table 1. There is clearly a shift in PL features by different excitation wavelengths which may correspond to excitation energy and the presence of quantum size effects [12]. With the consideration of optical gain, we investigated the spontaneous emission spectra (SE) of Quantum Dots (QDs) in both solution and solid sol-gel rods. A high-power picosecond laser system with a 355 nm laser source was utilized for excitation. The energy pumped ranged from 50 μ J to 1.5 mJ was used to prevent photobleaching of the solid sol-gel rod by the 355 nm laser source. Fig. 7 display the SE spectra of QDs in solution and sol-gel rod, respectively, under various excitation energies. As the excitation energy increases, the intensity of QDs in both solution and sol-gel rod also increases. However, the SE intensity of QDs in the sol-gel rod is more pronounced compared to the solution when pumped with the same excitation energy, as depicted in (Fig. 7). Additionally, there is a slight shift in the peak position of QDs in the solid sol-gel rod compared to the peak of QDs in the solution.

**Fig. 7.** Spontaneous emission spectra of QDs: a – solution; b – sol gel rod

For example, the spontaneous peak observed at 506 nm in the QDs solution of (Fig. 7 a) shifts to 500 nm in the solid sol-gel of (Fig. 7 b). The spontaneous emission of QDs in the solid sol-gel exhibits significant improvement under different excitation energies. The SE peak positions of the QDs in the composite sol-gel rod and solution are listed in Table 1.

Increasing of emission intensity of QDs in the rod with the variation of pump energy shows good stability of QD particles in a solid environment. Moreover, the uniformity of inhabitant and distribution of QDs particles in solid medium could produce a stable PL. The comparison of emission and SE peak of QDs in solution and solid sol-gel at excitation of 355 nm is shown in (Fig. 8).

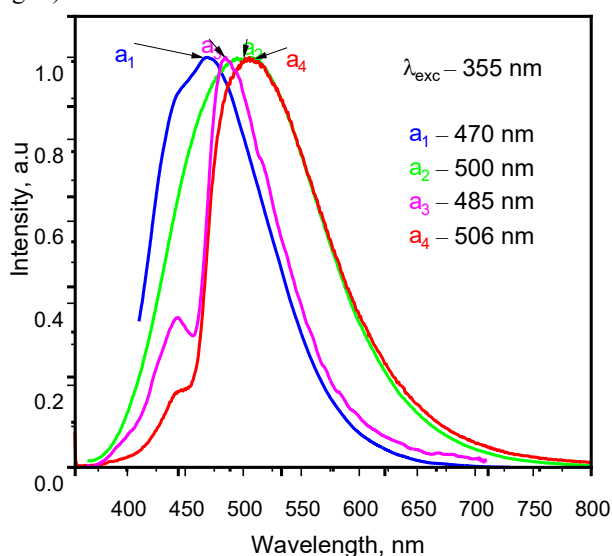


Fig. 8. Comparison of normalized emission and spontaneous emission peaks between QDs in solution and sol gel rod at 355 nm excitation wavelength

In Fig. 8, the emission peaks of QDs in sol-gel rod observed at a_1 –470 nm and a_3 –485 in solution. The SE peak at a_2 –500 nm and a_4 –506 nm of QDs are observed in sol-gel rod and solution respectively. No significant effect on SE peaks between QDs sol-gel solid and solution which is more or less 6 nm. Overall, the observed SE peak of QDs in solid rod upon the laser pump energy is quite stable.

Although the current SE peak does not satisfy the optical gain condition, it holds potential for future improvements by utilizing a higher density of QDs solution within such a solid rod. These findings suggest that a high-density QDs composite sol-gel rod could be a promising material for future studies in optical applications, potentially leading to stimulated emission or amplified spontaneous emission (ASE).

4. CONCLUSIONS

The CdS quantum dots composite rods were successfully prepared. Optical stability of QDs in solid sol gel rod was observed. PL property of the QDs composite rod was quite stable. The emission peaks and relative intensity of the QDs in both solution and sol gel rod were found to be influenced by the excitation wavelengths. No aggregate of QD particles in the solid environment was

observed. The significant spontaneous emission from QDs composite rod was exhibited under the laser pump energy. Present results revealed that addition of quantum dots in solid rod is quite possible without any degradation of optical property. It is highly expected that such QDs composite rod may be used as active media for the further testing of ASE if it employs a highly dense packed of QDs nanocomposites rod.

Acknowledgments

The researchers wish to extend their sincere gratitude to the Deanship of Scientific Research at the Islamic University of Madinah for the support provided to the Post-Publishing Program. The authors are thankful to Laser and Spectroscopy Lab, King Abdullah Institute for Nanotechnology, King Saud University, for providing the facility for experimental work.

REFERENCES

1. Pietryga, J.M., Schaller Werder, R.D.D., Stewart, M.H., Klimov, V.I., Hollingsworth, J.A. Pushing the Band Gap Envelope: Mid-infrared Emitting Colloidal PbSe Quantum Dots *Journal of the American Chemical Society* 126 (38) 2004: pp. 11752–11753. <https://doi.org/10.1021/ja047659f>
2. Duncan, T.V., Mendez Polanco Kim, M.A.Y., Park, S.J. Improving the Quantum Yields of Semiconductor Quantum Dots through Photoenhancement Assisted by Reducing Agents *Journal of Physical Chemistry C* 113 (18) 2009: pp. 7561–7566. <https://doi.org/10.1021/jp811245r>
3. Peng, X.J., Wickham Alivisatos, A.P. Kinetics of II-VI and III-V Colloidal Semiconductor Nanocrystal Growth: Focusing of Size Distributions *Journal of the American Chemical Society* 120 (21) 1998: pp. 5343–5344. <https://doi.org/10.1021/ja9805425>
4. Yu, W.W., Peng, X. Formation of High-Quality CdS and Other II-VI Semiconductor Nanocrystals in Noncoordinating Solvents: Tunable Reactivity of Monomers *Angewandte Chemie International Edition* 41 (13) 2002: pp. 2368–2371. [https://doi.org/10.1002/1521-73\(20020703\)41:13<2368::AID-ANIE2368>3.0.CO;2-G](https://doi.org/10.1002/1521-73(20020703)41:13<2368::AID-ANIE2368>3.0.CO;2-G)
5. Jasieniak, J., Califano, M., Watkins, S.E. Size-Dependent Valence and Conduction Band-Edge Energies of Semiconductor Nanocrystals *ACS Nano* 5 (7) 2011: pp. 5888–5902. <https://doi.org/10.1021/nn201681s>
6. Najm, A.S., Naeem, H.S., Majdi, H.S., Hasbullah, S.A., Hasan, H.A., Sopian, K., Bais, B., Al-Iessa, H.J., Dhahad, H.A., Ali, J.M., Sultan, A.J. An In-depth Analysis of Nucleation and Growth Mechanism of CdS Thin Film Synthesized by Chemical Bath Deposition (CBD) Technique *Scientific Report* 12 (15295) 2022: pp. 15295. <https://doi.org/10.1038/s41598-022-19340-z>
7. Colvin, V.L., Schlamp, M.C., Alivisatos, A.P. Light-emitting Diodes Made from Cadmium Selenide Nanocrystals and a Semiconducting Polymer *Nature* 370 1994: pp. 354–357. <https://doi.org/10.1038/370354a0>
8. Bansal, A.K., Antolini, F., Zhang, S., Stroea, L., Ortolani, L., Lanzi, M., Serra, E., Allard, S., Scherf, U., Samuel, I.D.W. Highly Luminescent Colloidal CdS Quantum Dots with Efficient Near Infrared

- Electroluminescence in Light-Emitting Diodes *Journal of Physical Chemistry C* 120 2016: pp. 1871–1880. <https://doi.org/10.1021/acs.jpcc.5b09109>
9. **Hasanirokh, K., Asgari, A., Mohammadi, S.** Fabrication of a Light-emitting Device Based on the CdS/ZnS Spherical Quantum Dots *Journal of the European Optical Society-Rapid Publications* 17 (26) 2021: pp. 1–10. <https://doi.org/10.1186/s41476-021-00173-8>
 10. **Darugar, Q., Qian, W., El-Sayed, M.A.** Observation of Optical Gain in Solutions of CdS Quantum Dots at Room Temperature in the Blue Region *Applied Physics Letter* 88 2006: pp. 261108. <https://doi.org/10.1063/1.2217138>
 11. **Whittaker, C.A., Perret, A., Fortier, C.W., Tardif, O.M., Lamarre, S.A., Morency, S., Larivière, D., Beaulieu, L., Messaddeq, Y., Allen, C.N.** Light-Generating CdSe/CdS Colloidal Quantum Dot-Doped Plastic Optical Fibers *ACS Applied Nano Materials* 3 (7) 2020: pp. 6478–6488. <https://doi.org/10.1021/acsnm.0c00946>
 12. **Schuler, A., Python, M., Valle del Olmo, M., de Chambrier, E.** Quantum Dot Containing Nanocomposite Thin Films for Photoluminescent Solar Concentrators *Solar Energy* 81 (9) 2007: pp. 1159–1165. <https://doi.org/10.1016/j.solener.2007.01.015>
 13. **Hamid, Z.A., Hassan, H.B., Hassan, M.A., Mourad, M.H., Anwar, S.** Deposition, Characterization, Performance of Cadmium Sulfide Quantum Dots Thin Films Using SILAR Technique for Quantum Dot Sensitized Solar Cell Applications *Key Engineering Materials* 835 2020: pp. 374–383. <https://doi.org/10.4028/www.scientific.net/KEM.835.374>
 14. **Sami, R., Ghazai, A.J.** Synthesis and Characterization of Nanostructural CdS Thin Film Using Spin Coating Technique for Photodetector Application *Journal of Nanostructures* 12 (2) 2022: pp. 405–413. <https://doi.org/10.22052/JNS.2022.02.016>
 15. **Kumar, A., Vasantha, R.** Optical and structural of Nanocrystalline CdS *Experimental and Theoretical Nanotechnology* 4 2002: pp. 201–208. <https://doi.org/10.56053/4.3.201>
 16. **Smyntyna, V.A., Skobeeva, V.M., Verheles, K.A., Malushin, N.V.** Influence of Technology on the Formation of Luminescence Centers in CdS Quantum Dots *Journal of Nano-Electronic Physics* 11 (3) 2019: pp. 05031 (4pp). [https://doi.org/10.21272/jnep.11\(5\).05031](https://doi.org/10.21272/jnep.11(5).05031)
 17. **Khan, M.N., Al Dwayyan, A.S., Al Hossain, M.S.** Morphology and Optical Properties of a Porous Silicon-Doped Sol-gel Host *Electronic Materials Letters* 9 (5) 2013: pp. 697–703. <https://doi.org/10.1007/s13391-013-2241-0>
 18. **Jianbin, H., Qinghong, D., Linlin, G.** The Preparation of Quantum Dot CdS Doped Silica Glass by the Improved Sol Gel Process *Acta Physico-Chemica Sinica* 14 (1) 1998: pp. 13–20. <https://doi.org/10.3866/PKU.WHXB19980104>
 19. **Thambidurai, M., Murugan, N., Muthukumarasamy, N., Agilan, S., Vasantha, S., Balasundaraprabhu, R.** Influence of the Cd/S Molar Ratio on the Optical and Structural Properties of Nanocrystalline CdS Thin Films *Journal of Materials Science and Technology* 26 (3) 2010: pp. 193–199. [https://doi.org/10.1016/S1005-0302\(10\)60032-1](https://doi.org/10.1016/S1005-0302(10)60032-1)
 20. **Khanna, R.K., Singh, N.** Light emitting CdS quantum dots in PMMA: Synthesis and Optical studies *Journal of Luminescence* 127 2007: pp. 474–482. <https://doi.org/10.1016/j.jlumin.2007.02.037>
 21. **Kang, K., Daneshvar, K.** CdS Quantum Dots in Hybrid Sol-gel Matrix; Absorption and Room-Temperature Photoluminescence *Journal of Applied Physics* 95 (2) 2004: pp. 646–648. <https://doi.org/10.1063/1.1633651>
 22. **Han, K., Yoon, S., Chung, W.J.** CdS and CdSe Quantum Dot-embedded Silicate Glasses for LED Color Converter *International Journal of Applied Glass Science* 6 (2) 2015: pp.103–108. <https://doi.org/10.1111/ijag.12115>
 23. **Khan, M.N., Aldabahi, A., Al Dwayyan, A.S.** Composite Rods Based on Nanoscale Porous Silicon in Sol Gel Silica and Ormosil Matrices for Light Emitting Applications *Journal of Sol-gel Science and Technology* 82 (2) 2017: pp. 551–562. <https://doi.org/10.1007/s10971-017-4309-z>
 24. **Khan, M.N., Al Dwayyan, A.S., Aldabahi, A.** Light Emitting Composite Rods Based on Porous Silicon in Ormosil and Polymer Matrices for Optical Applications *Optics and Laser Technology* 91 2017: pp. 203–211. <https://doi.org/10.1016/j.optlastec.2016.12.035>
 25. **Khan, M.N., Aldabahi, A., Almohammadi, A.** Investigation of Different Colloidal Porous Silicon Solutions and Their Composite Solid Matrix Rods by Optical Techniques *Electronic Materials* 47 (7) 2018: pp. 3576–3607. <https://doi.org/10.1007/s11664-018-6204-y>
 26. **Khan, M.N. Almohammadi, A.** Fabrication and Amplified Spontaneous Emission Behavior of FAPbBr₃ Perovskite Quantum Dots in Solid Polymer Rods *Materials Science-Poland* 40 (1) 2022: pp. 84–100. <https://doi.org/10.2478/msp-2022-0006>
 27. **Lisco, F., Kaminski, P.M., Abbas, A., Bass, K., Bowers, J.W., Claudio, G., Losurdo, M., Walls, J.M.** The Structural Properties of Cds Deposited by Chemical Bath Deposition and Pulsed Direct Current Magnetron Sputtering *Thin Solid Films* 582 2015: pp. 323–327. <https://doi.org/10.1016/j.tsf.2014.11.062>
 28. **Muniyappan, S., Solaiyammal, T., Keerthana, G.T., Vivek, P., Murugakoothan, P.** Influence of Annealing Temperature on Structural, Morphological and Optical Properties of CTAB Assisted Cadmium Sulphide (CdS) Quantum Dots: Promising Candidate for Quantum Dot Sensitized Solar Cell (QDSSC) Applications *Journal of Matererials Science: Materials in Electronics* 28 2017: pp. 11317–11324. <https://doi.org/10.1007/s10854-017-6924-4>
 29. **Lien, V.T.K., Ha, C.V., Ha, L.T., Dat, N.N.** Optical Properties of CdS and CdS/ZnS Quantum Dots Synthesized by Reverse Micelle Method *Journal of Physics: Conference Series* 187 (012028) 2019: pp. 1–6. <https://doi.org/10.1088/1742-6596/187/1/012028>
 30. **Fujii, T., Hisakawa, Y., Winder, E.J., Ellis, A.B.** Effect of Heat and Gases on the Photoluminescence of CdS QDs Confined in Silicate Glasses by Prepared by Sol-gel Method *Bulletin of the Chemical Society of Japan* 68 (6) 1995: pp. 1559–1564. <https://doi.org/10.1246/bcsj.68.1559>

