

# Mechanical and Microwave Absorption Properties of Exfoliated Graphite and Manganese Ferrite Nanoparticles on Polyvinylidene Fluoride Thin Films

Thamil Amudhu LEKKAIYAN BASKARAN<sup>1\*</sup>, Vimal Samsingh RAMALINGAM<sup>1</sup>,  
Esther Florence SUNDARSINGH<sup>2</sup>, Arun Prakash CHANDRAN<sup>3</sup>

<sup>1</sup> Department of Mechanical Engineering, Sri Sivasubramaniya Nadar College of Engineering, Chengalpattu–603110, Tamil Nadu, India

<sup>2</sup> Department of Electronics and Communication Engineering, Anna University, CEG Campus, Chennai–600025, Tamil Nadu, India

<sup>3</sup> Department of Production Technology, Madras Institute of Technology, Chennai–600044, Tamil Nadu, India

<http://doi.org/10.5755/j02.ms.38421>

Received 9 August 2024; accepted 26 September 2024

This study presents a simple and efficient method for the development of thin polymer composite films for use in absorbing electromagnetic waves at X-band frequencies. The thin film composites were fabricated by solution casting technique by incorporating the exfoliated graphite, and manganese ferrite nanoparticles into the polyvinylidene fluoride matrix. The composite film consisting of both 3 wt.% of MnFe<sub>2</sub>O<sub>4</sub> and exfoliated graphite/PVDF showed better absorption properties and achieved a minimum reflection loss of –30.54 at 9.62 GHz in the 8–12 GHz frequency range. This synergistic effect of the film was attributed to its  $\beta$ -phase formation, multiple-reflection-absorption effect, and the conduction of fillers at their interfaces. Finally, the mechanical and absorption characteristics of the fabricated thin film composites were also investigated. The results indicated that these composite films hold potential for use in microwave absorption applications in the X band.

**Keywords:** microwave absorption, X band absorbers, solution casting technique, thin films, mechanical properties.

## 1. INTRODUCTION

In recent years, concern over microwave absorbers has significantly increased due to the growing prevalence of radar technology. Microwave absorbers are widely used in stealth aircraft operations, particularly in the X band (8–12 GHz). Polyvinylidene fluoride (PVDF) based composites were studied extensively for their lightweight, flexibility, mechanical durability, and environmental friendliness. Consequently, addressing and mitigating undesirable electromagnetic radiation became an essential concern. To improve the  $\beta$ -phase of the PVDF matrix, various nanofillers such as ferrites and carbon materials were incorporated into composite materials. This incorporation of nanofillers improved the microwave absorption performance of PVDF-based composites. Among these nanofillers, exfoliated graphite (EG) was particularly noted for its excellent dispersion qualities, large surface area, and high conductivity, making it a highly desirable material for microwave absorption. EG's superior electrical conductivity was attributed to its lower oxygen content compared to other types of graphite [4, 5]. The presence of OH and COOH groups on the surface of EG enables more physical and chemical interactions with polymers, resulting in unique mechanical and thermal properties [6–8]. Ferrites are known to be effective in absorbing electromagnetic waves due to their exceptional wave absorption capabilities, abundance of raw materials, and low cost [9–11]. Among the ferrites, Manganese ferrite

(MnFe<sub>2</sub>O<sub>4</sub>), the most preferred ferrite material among researchers for microwave absorption due to its high surface area and low density. Additionally, MnFe<sub>2</sub>O<sub>4</sub> has high magnetic permeability, resulting in stronger magnetic properties and higher wave absorption capacity [12, 13]. It can be used in various forms such as nanoparticles, nanostructures, and thin films, with each having unique properties such as continuous anisotropy, size-dependent magnetization saturation, and a high Curie temperature, further enhancing its suitability for electromagnetic wave absorption applications [14, 15]. Recent studies have focused on magnetic nanoparticles combined with PVDF nanocomposite films have emerged as highly promising candidates for various fields [16]. For decades, microwave absorbers have been integral to military uses and other applications like antenna pattern shaping and radar cross-section reduction. Traditional microwave absorbers, such as ferrite, carbon materials, and magnetic nanocomposites, are typically powder materials with high reflection loss [17]. However, these conventional materials are often heavy and inflexible, limiting their effectiveness in lightweight structures like aircraft. The significance of this work lies in its demonstration of improved microwave absorption and mechanical properties through the synergistic use of both carbon and magnetic fillers. Several studies have concentrated separately on microwave absorption and mechanical characteristics, herein this composite offers a balanced performance in both properties. To address these limitations, microwave absorbing materials with

\* Corresponding author: T.A. Lekkaian Baskaran  
E-mail: [thamil18008@mech.ssn.edu.in](mailto:thamil18008@mech.ssn.edu.in)

electroactive polymers offer a solution-by-solution casting method. This approach produces thin, flexible nanocomposite films with excellent frequency responses in the GHz range. Therefore, extensive research is needed on microwave absorption materials. In particular, nanoparticles like carbon and magnetic particles combined with PVDF nanocomposites showed great potential in the X-band frequency range (8–12 GHz) [18]. Thus, this work presents a thorough analysis of the electromagnetic wave absorption characteristics of exfoliated graphite and manganese ferrite embedded in a PVDF matrix. This study was tested using vector network analysis, X-ray diffraction, and scanning electron microscopy for microwave absorption at X-band frequency (8–12 GHz). The combination of EG and  $\text{MnFe}_2\text{O}_4$  together has a synergistic effect that improves the electrical and magnetic characteristics of thin films. These thin film composites could be employed in a variety of defense and electronic sectors to reduce electromagnetic interference. Furthermore, the nanocomposites developed in this study can be used to construct enclosures for electronic devices and shield them from unwanted electromagnetic waves. The research findings will provide valuable insights into the optimal conditions and significant contributions that can enhance the absorption of microwaves in the prepared composite thin films.

## 2. EXPERIMENTAL PROCEDURE


Polyvinylidene fluoride (PVDF) was purchased from Thermo Fisher Scientific Pvt Ltd. Exfoliated graphite (EG) and Manganese ferrite ( $\text{MnFe}_2\text{O}_4$ ) nanoparticles were obtained from Nano research lab, India. Dimethylformamide (DMF) was purchased from Merck Ltd. The PVDF/EG/ $\text{MnFe}_2\text{O}_4$  composite thin films were fabricated by a simple technique called the solution casting method. Initially, the PVDF powder is dissolved in DMF solution for 3 hrs by using a magnetic stirrer. Then EG nanoparticles were then added to PVDF/DMF solution and mixed well through a magnetic stirrer for 2 hours at 60 °C. And then  $\text{MnFe}_2\text{O}_4$  nanoparticles were added to the prepared PVDF/EG solution and stirred for 2 hours at 60 °C to get uniform distribution. Finally, the solution was poured into a Petri dish and cast into films at 60 °C for 8 hrs. Likewise, the different composite thin films were fabricated for the various concentrations of the fillers as tabulated in Table 1. The aggregation caused by PVDF polymer could be reduced by increasing the stirring time to get the homogenous polymeric solution and also lowering the filler concentrations.

**Table 1.** Composition of the fabricated thin film

Sl.No.	Sample designations	Material combinations, wt.%
1	A	Pure PVDF
2	B	3 wt.% EG/PVDF
3	C	1 wt.% of $\text{MnFe}_2\text{O}_4$ –3 wt.% EG/PVDF
4	D	3 wt.% of $\text{MnFe}_2\text{O}_4$ –3 wt.% EG/PVDF
5	E	5 wt.% of $\text{MnFe}_2\text{O}_4$ –3 wt.% EG /PVDF

## 3. RESULTS AND DISCUSSION


The XRD patterns revealed the presence of distinct crystalline phases within the PVDF sample. As illustrated in Fig. 1, the XRD spectrum observed the electrically active polar  $\beta$ -phase at 20.34° and 36.24°, the non-polar  $\alpha$ -phase at 18.54° and 26.5°, and the polar  $\gamma$ -phase at 39.02°. Incorporating carbonaceous and ferrite filler into the PVDF matrix, indicated an increase in the composite's  $\alpha$  and  $\beta$ -phases which led to improved dielectric characteristics [16–18]. The PVDF's polar phase nucleation was influenced by the interactions near the EG/ $\text{MnFe}_2\text{O}_4$ /PVDF interfaces. This phenomenon of interfacial interaction influences the crystallization behaviour and overall properties of thin films. The crystallinity of the composite thin films is enhanced due to the formation of cationic complexes with the functional group of PVDF, which confirms the intercalation of EG with the PVDF polymer system.

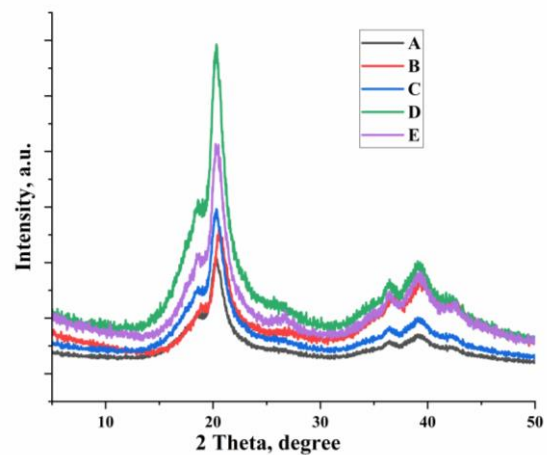

**Fig. 1.** XRD patterns of the thin films: A – pure PVDF; B – 3 wt.% EG/PVDF; C – 1 wt.% of  $\text{MnFe}_2\text{O}_4$  and 3 wt.% EG/PVDF; D – 3 wt.% of  $\text{MnFe}_2\text{O}_4$  and 3 wt.% EG/PVDF; E – 5 wt.% of  $\text{MnFe}_2\text{O}_4$  and 3 wt.% EG /PVDF


The SEM images shown in Fig. 2 revealed the crystallization of the  $\beta$ -phase within the PVDF films. The SEM images of samples reveal well-defined, uniform, and densely packed EG and manganese iron oxide particles within the PVDF composite films. In Fig. 2 c sample D, where the uniform distribution of nanoparticles on the surface serves as a distinct indicator of  $\beta$ -phase crystallization whereas in Fig. 2 d, sample E shows the presence of agglomeration, voids, and pores due to the high percentage of filler particles.

The incorporation of exfoliated graphite nanoparticles into the PVDF matrix enhanced the polar  $\beta$ -phase of PVDF. These nanoparticles served as nucleation centers, influencing the alignment of dipoles within the PVDF structure. The increased number of nucleation sites promoted the development of the  $\beta$  phase in the composite thin films. For consistent and efficient performance of these thin composite films, it was crucial to maintain a uniform dispersion of reinforcements such as EG and  $\text{MnFe}_2\text{O}_4$  particles to get synergistic effects and a continuous conductive network. However, particle agglomeration led to stress concentration, which negatively impacted the film's tensile properties [19–21].

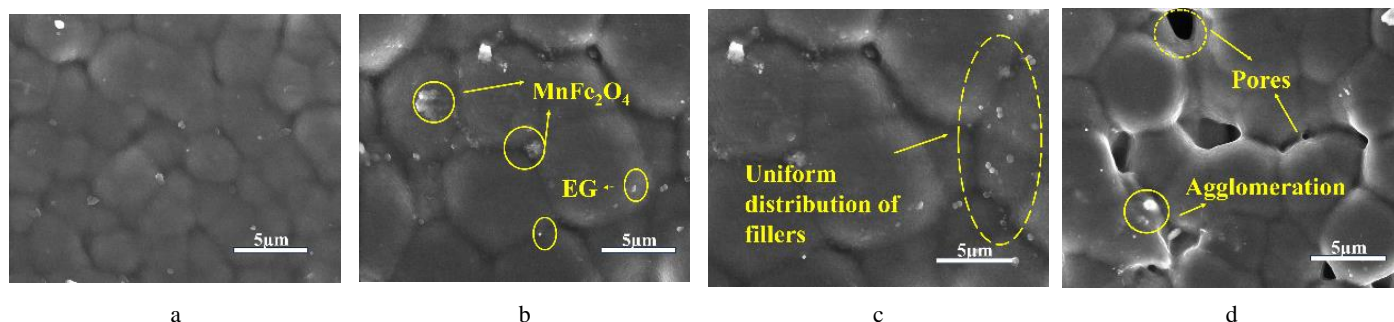

**Fig. 2.** Microstructures of the thin films (a) 3 wt. % EG /PVDF (b) 1 wt. % of  $\text{MnFe}_2\text{O}_4$  -3 wt. % EG /PVDF (c) 3 wt. % of  $\text{MnFe}_2\text{O}_4$  -3 wt. % EG /PVDF (d) 5 wt. % of  $\text{MnFe}_2\text{O}_4$  -3 wt. % EG /PVDF

The Vector Network Analyzer (Agilent N9917A) was connected to the two horn antennas for the analysis of the reflected microwaves [22–24]. Stress induces the polymer chain to become oriented, which is essential for the transition to PVDF's  $\beta$  phase [13–15]. The maximum tensile strength of samples B-E is 26.65, 28.24, 32.16, and 29.21 MPa respectively, which are compared to the pure PVDF film (24.52 MPa) as shown in Fig. 4. This microwave performance was attributed to the broad surface area, high electrical conductivity, homogeneous dispersion and magnetic response of  $\text{MnFe}_2\text{O}_4$  nanoparticles, which caused electric and magnetic loss. Additionally, dielectric loss was identified as the primary contributor to electromagnetic loss in thin films because of the presence of EG nanoparticles.

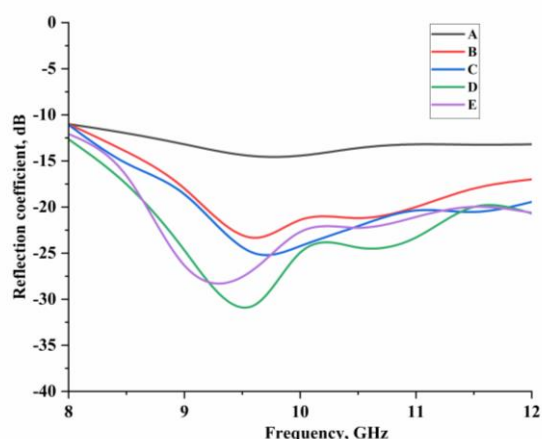


**Fig. 3.** Reflection coefficient of the thin films at 8–12 GHz


In that, two horn antennas were used as a receiver and transmitter, positioned for bistatic radar operations in an anechoic chamber setup. The results showed reduced

reflection for PVDF films with carbon and magnetic fillers for all concentrations. Notably, the composite with 3 wt.% of both  $\text{MnFe}_2\text{O}_4$  and EG in the PVDF matrix demonstrated microwave absorption with a minimum reflection loss of  $-30.54$  at  $9.62$  GHz in the X band in Fig. 3.

The absorption of microwaves is determined by the interaction between electric and magnetic dipoles within the material. The microwave absorption behavior was attributed to the synergistic effect of exfoliated graphite,  $\text{MnFe}_2\text{O}_4$ , and PVDF, leading to enhanced dielectric and magnetic dissipation. Stress induces the polymer chain to become oriented, which is essential for the transition to PVDF's  $\beta$  phase [25, 26]. The maximum tensile strength of samples B–E is 26.65, 28.24, 32.16, and 29.21 MPa respectively, which are compared to the pure PVDF film (24.52 MPa) as shown in Fig. 4.

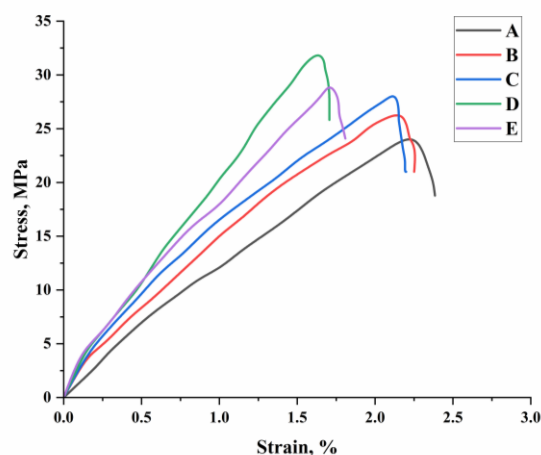

**Fig. 4.** Tensile properties of the PVDF composite thin films

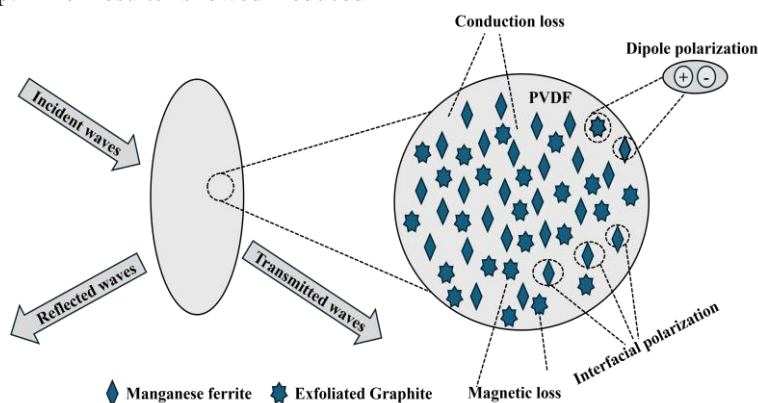

**Fig. 5.** Schematic diagram of the microwave mechanism of the fabricated PVDF composites

The microwave mechanism of the fabricated PVDF composite thin films is illustrated in the schematic diagram in Fig. 5. The significance of the enhanced microwave absorption achieved through the synergistic use of EG and MnFe<sub>2</sub>O<sub>4</sub>. These fillers improved the dielectric loss, conduction loss, interfacial polarisation, and magnetic loss which offered a balanced performance in microwave absorption properties. The increased polarizability in the EG/MnFe<sub>2</sub>O<sub>4</sub>/PVDF nanocomposite thin films (B, C, D & E) because of the presence of negatively charged fluorine atoms and PVDF was influenced by electrostatic interactions with EG and MnFe<sub>2</sub>O<sub>4</sub>, making it more polarized compared to the pure PVDF sample (A).

#### 4. CONCLUSIONS

In this study, we present an effective and simple method to fabricate microwave absorber composite thin films using a polyvinylidene fluoride (PVDF) matrix with exfoliated graphite and manganese ferrite nanoparticles for microwave absorption. Furthermore, the proposed thin film composite absorber of 3 wt. % of both MnFe<sub>2</sub>O<sub>4</sub>/EG in PVDF has a minimum reflection loss of -30.54 at 9.62 GHz in the X band. Moreover, the maximum tensile strength of samples B-E is 26.65, 28.24, 32.16 and 29.21 MPa respectively, which are compared to the pure PVDF film. Thus, the thin film exhibited improved mechanical properties which makes it suitable for X-band applications. The results indicated that these composite films hold potential for use in electromagnetic wave absorption applications, particularly in stealth aircraft industries. Further studies in this research will be focused on identifying superior substitution materials for the matrix and reinforcements. Moreover, simulations of these composites will be investigated to improve microwave absorption.

#### REFERENCES

1. Saha, S., Chakraborty, T., Saha, A., Das, S., Pramanik, G., Pradhan, A.K., Chakraborty, C., Das, S., Sutradhar, S. A Multi-Layer Design of Hexaferrite Decorated Graphene Derivatives Incorporated PVDF Nanocomposite Films; Understanding the Role of GO/Rgo for Outstanding Electromagnetic Wave Absorption at Microwave Frequencies *Carbon* 220 2024: pp.118829. <https://doi.org/10.1016/j.carbon.2024.118829>
2. John, F.A., Thomas, P., Jacob, G., Jose, A.J. Effective Interactions and Dielectric Study of Polymer Nanocomposite Thin Films of Polyvinylidene Fluoride and Graphene Oxide *Composite Interfaces* 31 (1) 2024: pp. 77–97. <https://doi.org/10.1080/09276440.2023.2232979>
3. Li, X., Ma, C., Chi, H., Song, M., Lu, S., Dai, P. Enhancing Thermal Conductivity and Electromagnetic Shielding Performance of Ni-CNT/ Al<sub>2</sub>O<sub>3</sub>/ PVDF Composite Film with a Multi-layered Structure *Composites Science and Technology* 251 2024: pp. 110589. <https://doi.org/10.1016/j.compscitech.2024.110589>
4. Iftikhar, M., Shahzad, F., Iqbal, A., Mumtaz, M., Ahmad, I., Hassan, T. Koo, C.M. Synergistic Terahertz Shielding Effects of Electrically Conductive MXene and Shape-controlled Magnetic Nickel in Polyvinylidene Fluoride (PVDF) Composites *Journal of Alloys and Compounds* 989 2024: pp. 174306. <https://doi.org/10.1016/j.jallcom.2024.174306>
5. Parida, S., Kumar Nath, N., Parida, R.K., Parida, B.N., Nayak, N.C. Effect of Foaming on the Electromagnetic Interference-shielding Performance of Exfoliated Graphite Nanoplatelets-filled EVA/EOC Blend Composites in the S-band Region *Materials Advances* 5 (6) 2024: pp. 2597–2605. <https://doi.org/10.1039/D3MA00989K>
6. Fang, J., Chen, C., Qi, H., Zhang, J., Hou, X., Pan, L., Wang, X. Flexible Multilayered Poly(vinylidene fluoride)/ Graphene-Poly(vinylidene fluoride) Films for Efficient Electromagnetic Shielding *ACS Applied Nano Materials* 6 (8)2023: pp. 6858–6868. <https://doi.org/10.1021/acsanm.3c00574>
7. Thakur, N. Nanostructured MnFe<sub>2</sub>O<sub>4</sub> Anchored on Graphene Oxide and Reduced Graphene Oxide Sheets for Effective Regulation of Microwave Absorption Performance *Powder Technology* 410 2022: pp. 117895. <https://doi.org/10.1016/j.powtec.2022.117895>
8. Yadav, R.S., Jamatia, T., Kuřitka, I., Vilčáková, J., Škoda, D., Urbánek, P., Machovský, M., Masař, M., Urbánek, M., Kalina, L., Havlica, J. Excellent, Lightweight and Flexible Electromagnetic Interference Shielding Nanocomposites Based on Polypropylene with MnFe<sub>2</sub>O<sub>4</sub> Spinel Ferrite Nanoparticles and Reduced Graphene Oxide *Nanomaterials* 10 (12) 2020: p. 2481. <https://doi.org/10.3390/nano10122481>
9. Amudhu, L.B.T., Samsingh, R.V., Florence, S.E., Abirami, B.S. Novel Radar Absorbing Material Using Resistive Frequency Selective Surface-Based Polymer Composites for Enhanced Broadband Microwave Absorption *Proceedings of the Institution of Mechanical Engineers, Part L: Journal of Materials: Design and Applications* 237 (10) 2023: pp. 2115–2125. <https://doi.org/10.1177/14644207231169362>
10. Fu, B., Ren, P., Guo, Z., Zong, Z., Jin, Y., Dai, Z., Ren, F. Preparation of Porous Graphene Nanosheets/Carbon Nanotube/Polyvinylidene Fluoride (GNS/CNT/PVDF) Composites for High Microwave Absorption in X-band *Journal of Materials Science: Materials in Electronics* 32 2021: pp. 9611–9622. <https://doi.org/10.1007/s10854-021-05623-0>
11. Meisak, D., Macutkevicius, J., Plyushch, A., Kuzhir, P., Selskis, A., Banys, J. Dielectric Relaxation in the Hybrid Epoxy/MWCNT/MnFe<sub>2</sub>O<sub>4</sub> Composites *Polymers* 12 (3) 2020: pp. 697. <https://doi.org/10.3390/polym12030697>
12. Amudhu, L.T., Samsingh, R.V., Florence, S.E., Abirami, B.S. Low-profile Polymer Composite Radar Absorber Embedded with Frequency Selective Surface *IEEE Transactions on Components, Packaging and Manufacturing Technology* 13 (3) 2023: pp. 444–447. <https://doi.org/10.1109/TCPMT.2023.3257310>
13. Zhao, B., Deng, J., Zhao, C., Wang, C., Chen, Y.G., Hamidinejad, M., Li, R., Park, C.B. Achieving Wideband Microwave Absorption Properties in PVDF Nanocomposite Foams with an Ultra-low MWCNT Content by Introducing a Microcellular Structure *Journal of Materials Chemistry C* 8 (1) 2020: pp. 58–70. <https://doi.org/10.1039/C9TC04575A>
14. Saha, S., Chakraborty, T., Saha, A., Das, S., Pramanik, G., Pradhan, A.K., Chakraborty, C., Das, S., Sutradhar, S. A Multi-layer Design of Hexaferrite Decorated Graphene Derivatives Incorporated PVDF Nanocomposite Films, Understanding the Role of GO/rGO for Outstanding Electromagnetic Wave Absorption at Microwave Frequencies *Carbon* 220 2024: pp. 118829.

<https://doi.org/10.1016/j.carbon.2024.118829>

15. **Thamil Amudhu, L.B., Samsingh, R.V., Florence, S.E., Sathyanarayan, S.** Performance Assessment of Nanofiber Integrated Polymer Composite as Electromagnetic Wave Absorber *Journal of Inorganic and Organometallic Polymers and Materials* 2024: pp. 1–12.  
<https://doi.org/10.1007/s10904-023-02969-2>
16. **Cheng, H., Wei, S., Ji, Y., Zhai, J., Zhang, X., Chen, J., Shen, C.** Synergetic Effect of Fe<sub>3</sub>O<sub>4</sub> Nanoparticles and Carbon on Flexible Poly (Vinylidene Fluoride) Based Films with Higher Heat Dissipation to Improve Electromagnetic Shielding *Composites Part A: Applied Science and Manufacturing* 121 2019: pp. 139–148.  
<https://doi.org/10.1016/j.compositesa.2019.03.019>
17. **Li, N., Huang, G.W., Li, Y.Q., Xiao, H.M., Feng, Q.P., Hu, N., Fu, S.Y.** Enhanced Microwave Absorption Performance of Coated Carbon Nanotubes by Optimizing the Fe<sub>3</sub>O<sub>4</sub> Nanocoating Structure *ACS Applied Materials & Interfaces* 9 (3) 2017: pp. 2973–2983.  
<https://doi.org/10.1021/acsami.6b13142>
18. **Feng, J., Hou, Y., Wang, Y., Li, L.** Synthesis of Hierarchical ZnFe<sub>2</sub>O<sub>4</sub>@ SiO<sub>2</sub>@ RGO Core-shell Microspheres for Enhanced Electromagnetic Wave Absorption *ACS Applied Materials & Interfaces* 9 (16) 2017: pp. 14103–14111.  
<https://doi.org/10.1021/acsami.7b03330>
19. **Wen, F., Zhang, F., Liu, Z.** Investigation on Microwave Absorption Properties for Multiwalled Carbon Nanotubes/Fe/Co/Ni Nano Powders as Lightweight Absorbers *The Journal of Physical Chemistry C* 115 (29) 2011: pp. 14025–14030.  
<https://doi.org/10.1021/jp202078p>
20. **Dinakaran, K., Narayanasamy, K., Theerthagiri, S., Peethambaram, P., Krishnan, S., Roy, D.** Microwave Absorption and Dielectric Behavior of Lead Sulfide-Graphene Composite Nanostructure Embedded Polyvinylidenedifluoride Thin Films *International Journal of Polymer Analysis and Characterization* 27 (5) 2022: pp. 277–288.  
<https://doi.org/10.1080/1023666X.2022.2067958>
21. **Du, Y.H., Gao, N., Li, M.D., Wang, L., Wang, G.S.,** Preparation and Microwave Absorption Properties of NixSy/PVDF Nanocomposites *Frontiers in Materials* 7 2020: pp. 80.  
<https://doi.org/10.3389/fmats.2020.00080>
22. **Ponraj, B., Deepa, S.** Absorption-dominant Microwave Shielding Properties of SnO 2Fe<sub>2</sub> 8O<sub>4</sub>-graphite-PVDF Ternary Nanocomposite Films *Journal of Physics D: Applied Physics* 55 (9) 2022: pp. 095002.  
<https://doi.org/10.1088/1361-6463/ac38e2>
23. **Dani, S., Channabasavanna, P.N., Kulkarni, S., Manohara, S.R., Udayakumar, K.** The Electromagnetic Interference Shielding Effectiveness and Dielectric Response of PVDF-ntio2nanocomposites Thin Films *Trends in Sciences* 19 (21) 2022: pp. 3046–3046.  
<https://doi.org/10.48048/tis.2022.3046>
24. **Siddiki, S.H., Das, S., Verma, K., Dashairya, L., Das, S., Thakur, V.K., Nayak, G.C.** Substituted Nickel Ferrite Coated MWCNT/PVDF Based Epoxy Nanocomposite for Microwave Absorption *Ceramics International* 48 (20) 2022: pp. 30260–30271.  
<https://doi.org/10.1016/j.ceramint.2022.06.299>
25. **Zhao, B., Deng, J., Zhao, C., Wang, C., Chen, Y.G., Hamidinejad, M., Li, R., Park, C.B.,** Achieving Wideband Microwave Absorption Properties in PVDF Nanocomposite Foams with an Ultra-low MWCNT Content by Introducing a Microcellular Structure *Journal of Materials Chemistry C* 8 (1) 2020: pp. 58–70.  
<https://doi.org/10.1039/C9TC04575A>
26. **Amudhu, L.B., Thamil, R., Vimal Samsingh, S., Esther Florence, S., Vinoth, T.** Enhanced microwave absorption and mechanical performance of polyvinylidene fluoride thin films embedded with novel activated carbon and manganese ferrite *Polymer Composites* 45 (16) 2024: pp. 15034–15045.  
<https://doi.org/10.1002/pc.28819>



© Lekhaiyan Baskaran et al. 2025 Open Access This article is distributed under the terms of the Creative Commons Attribution 4.0 International License (<http://creativecommons.org/licenses/by/4.0/>), which permits unrestricted use, distribution, and reproduction in any medium, provided you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons license, and indicate if changes were made.